ARMY RESEARCH LABORATORY

Predicted Discharge Rate for γ/β-MnO$_2$ versus λ-MnO$_2$

Jeff Wolfenstine

Contents

Figure

Recently, λ-MnO$_2$ has been proposed as an alternative cathode to γ/β-MnO$_2$ in Li/MnO$_2$ primary batteries [1]. One suggested advantage of λ-MnO$_2$ over γ/β-MnO$_2$ is its faster discharge rate at both room and low temperatures [1]. For the MnO$_2$ cathode, its discharge rate I is a function of its lithium diffusivity D and particle size d:

$$I \alpha D/d \ . \tag{1}$$

Equation (1) shows that increasing lithium diffusivity and/or decreasing the particle size leads to an increase in the discharge rate. Equation (1) also shows that if two different materials of the same particle size have a difference in discharge rates for the same experimental conditions (i.e., electrolyte), this difference must result from the difference in their D values. In this note, my goal is to determine whether a switch from a γ/β-MnO$_2$ cathode to a λ-MnO$_2$ cathode causes an increase in the discharge rate in the Li/MnO$_2$ system, as a result of a difference in the diffusivity D of the two materials. This comparison is made at room temperature only, since no low-temperature data for D in γ/β-MnO$_2$ or λ-MnO$_2$ currently exist.

Lithium diffusivity in γ-MnO$_2$ [2,3], β-MnO$_2$ [3], and λ-MnO$_2$ [4] at room temperature is plotted in figure 1. The figure includes, for λ-MnO$_2$, a data point at 3×10^{-11} cm^2/s (which was measured for LiMn$_2$O$_4$ [5]) and one at 4×10^{-11} cm^2/s (measured for Li$_{0.4}$MnO$_4$ [6]). These two points are plotted for λ-MnO$_2$ because Li$_x$Mn$_2$O$_4$ has the same structure as λ-MnO$_2$ [7,8], and Guyomard and Tarascon [4] have shown that the diffusion coefficient of lithium in Li$_x$Mn$_2$O$_4$ is independent of lithium composition x, for x from 0 to 1. Thus, the D values shown in figure 1 for LiMn$_2$O$_4$ ($x = 1$) and Li$_{0.4}$MnO$_4$ ($x = 0.4$) should correspond to lithium diffusivity in λ-MnO$_2$ ($x = 0$). The figure also includes lithium diffusivity values for γ-MnO$_2$ and β-MnO$_2$ produced from acid digestion of LiMn$_2$O$_4$ (filled symbols) [3].

Figure 1 suggests several important points. First, D in γ-MnO$_2$ is greater than D in β-MnO$_2$ (about a factor of 5 higher, if we consider only the open symbols). This is expected because the number of (2×1) channels decreases as the MnO$_2$ structure transforms from γ to β [8–10]. It has been suggested that lithium diffusivity is faster in the (2×1) channels than in (1×1) channels [10]. Hence, lithium diffusivity should decrease as the number of (2×1) channels decreases, which agrees with the data shown in figure 1. A similar trend is also observed in γ-MnO$_2$ and β-MnO$_2$ produced from acid digestion of LiMn$_2$O$_4$ (filled symbols).

A second observation from figure 1 is that two of the data points for λ-MnO$_2$, although from different research groups [5,6], are in excellent agreement with each other. However, there is a significant difference in D (about a factor of 25 to 30) between these data and the third data point (from Guyomard and Tarascon [4]). Reasons for this difference are not yet known. Since lithium diffusivity can be affected by impurities, it may be

1

Figure 1. Lithium diffusivity in γ-MnO$_2$ [2,3], β-MnO$_2$ [3], and λ-MnO$_2$ [4–6] at room temperature.
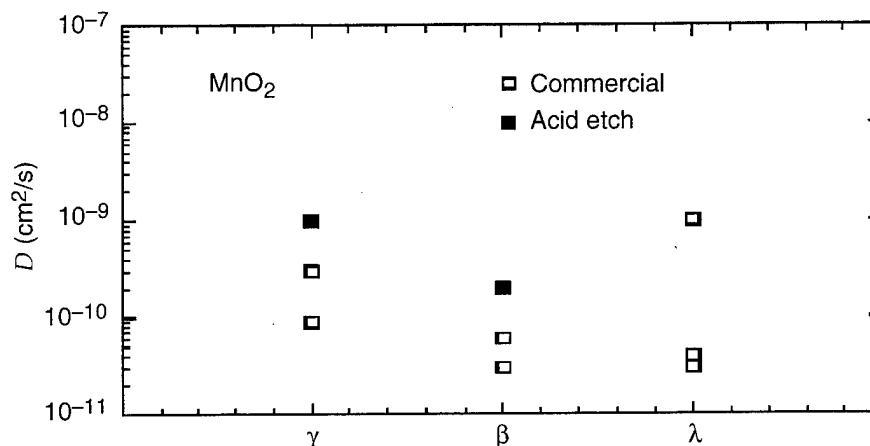
that material variations account for this difference [8]. However, the impurities and concentration for the three different materials were not given, so this suggestion cannot be confirmed.

The data in figure 1 can be used to determine whether (at room temperature) an increase in the discharge rate in Li/MnO$_2$ batteries is likely to occur as a result of a switch from γ/β-MnO$_2$ to λ-MnO$_2$ cathodes. The currently used γ/β-MnO$_2$ is a combination of γ-MnO$_2$ and β-MnO$_2$. Diffusivity D for γ/β-MnO$_2$ (open symbols) is about 1×10^{-10} cm^2/s. (This value is based on a 50 vol.% γ-MnO$_2$ and 50 vol.% β-MnO$_2$ mixture.) I compare D for γ/β-MnO$_2$ (1×10^{-10} cm^2/s) to two values of D for λ-MnO$_2$: 4×10^{-10} and 1×10^{-9} cm^2/s. (I choose these two values because of the discrepancy in the data for λ-MnO$_2$, discussed earlier.) If $D = 4 \times 10^{-10}$ cm^2/s for λ-MnO$_2$, the value for γ/β-MnO$_2$ is about 2.5× higher: $D = 1 \times 10^{-10}$ cm^2/s. Thus, according to equation (1), a *decrease* in the discharge current is predicted if λ-MnO$_2$ is used instead of γ/β-MnO$_2$ of equal particle size. If $D = 1 \times 10^{-9}$ cm^2/s for λ-MnO$_2$, the value of D of γ/β-MnO$_2$ is about 10× lower: 1×10^{-10} cm^2/s. In this case, according to equation (1), changing from γ/β-MnO$_2$ to λ-MnO$_2$ of the same particle size will lead to a maximum *increase* in the discharge rate of about an order of magnitude. Unfortunately, without more experimental data for λ-MnO$_2$, it is impossible to determine which is the correct D value for λ-MnO$_2$. In any case, the results reveal that the maximum increase in discharge rate at room temperature that can be achieved by switching from γ/β-MnO$_2$ to λ-MnO$_2$ of the same particle size is about an order of magnitude.

A third observation from figure 1 is that γ-MnO$_2$ and β-MnO$_2$ produced from acid digestion (filled symbols) have a higher lithium diffusivity than γ-MnO$_2$ and β-MnO$_2$ produced by standard commercial methods (open symbols). Figure 1 shows that for both γ-MnO$_2$ and β-MnO$_2$, the D values for these materials when produced by acid digestion is higher than the D values when they are prepared by commercial methods. Among several possible explanations for this observation are differences in impurities

and in structural water content. Since the impurities and their concentrations are not given, I cannot address this possibility. However, we know that the structural water content for the materials formed by acid digestion is about a factor of 10× lower than that for the materials prepared by commercial methods [3]. It is possible that the removal of structural water leads to more sites for lithium to occupy and move to and hence a higher D. More experimental work is required to confirm this suggestion. In any case, since γ-MnO_2 and β-MnO_2 produced by acid digestion have a higher D than commercially prepared γ-MnO_2 and β-MnO_2, acid digestion may be a method of increasing the D in MnO_2. One could speculate that λ-MnO_2 prepared from acid digestion of $LiMn_2O_4$ will also exhibit a higher D than λ-MnO_2 prepared by the more common electrochemical titration of $LiMn_2O_4$ (the method used to prepare the λ-MnO_2 shown in figure 1 [4]). At present, no low-temperature data for D in γ/β-MnO_2 or λ-MnO_2 exist, and hence no comparisons can be made.

The results of the comparisons presented here suggest the following:

(1) Switching from γ/β-MnO_2 to λ-MnO_2 of equal particle size will lead to a maximum increase in the discharge rate at room temperature of about an order of magnitude.

(2) More experimental data at both room and low temperatures are needed for D in γ/β-MnO_2 and λ-MnO_2 before we can accurately predict whether an increase in discharge rate will occur as a result of switching from γ/β-MnO_2 to λ-MnO_2 in the Li/MnO_2 system.

(3) When formed by acid digestion, γ-MnO_2 and β-MnO_2 have a higher D and hence a faster discharge rate than when produced by commercial methods. This difference may be a result of the lower structural water content in materials formed by acid digestion.

References

1. D. Chua, private communication.

2. J. Vondrak, I. Jakubec, and J. Bludska, *J. Power Sources* **14** (1986), 141.

3. M. M. Thackeray, A. de Kock, and L. A. de Piccotto, *J. Power Sources* **26** (1989), 355.

4. D. Guyomard and J. M. Tarascon, *J. Electrochem. Soc.* **139** (1992), 937.

5. B. J. Johnson, D. H. Doughty, J. A. Voigt, and T. J. Boyle, *J. Power Sources* **68** (1997), 634.

6. P. G. Dickens and G. J. Reynolds, *Solid State Ionics* **5** (1981), 331.

7. J. C. Hunter, *J. Solid State Chem.* **39** (1981), 142.

8. M. M. Thackeray, *Prog. Solid State Chem.* **25** (1997), 1.

9. Y. Shao-Horn, S. A. Hackney, and B. C. Cornilsen, *J. Electrochem. Soc.* **144** (1997), 3147.

10. M. M. Thackeray, M. H. Rossouw, R. J. Gummow, D. C. Lilies, K. Pearce, A. de Kock, W.I.F. David, and S. Hull, *Electrochim. Acta* **38** (1993), 1259.

Distribution

Admnstr
Defns Techl Info Ctr
Attn DTIC-OCP
8725 John J Kingman Rd Ste 0944
FT Belvoir VA 22060-6218

Ofc of the Secy of Defns
Attn ODDRE (R&AT)
The Pentagon
Washington DC 20301-3080

Ofc of the Secy of Defns
Attn OUSD(A&T)/ODDR&E(R) R J Trew
3080 Defense Pentagon
Washington DC 20301-7100

Advry Grp on Elect Devices
Attn Documents
Crystal Sq 4 1745 Jefferson Davis Hwy Ste 500
Arlington VA 22202

AMCOM MRDEC
Attn AMSMI-RD W C McCorkle
Redstone Arsenal AL 35898-5240

CECOM Night Vsn/Elect Sensors Dirctrt
Attn AMSEL-RD-NV-D
FT Belvoir VA 22060-5806

Commander
CECOM R&D
Attn AMSEL-IM-BM-I-L-R Stinfo Ofc
Attn AMSEL-IM-BM-I-L-R Techl Lib
Attn AMSEL-RD-AS-BE E Plichta
FT Monmouth NJ 07703-5703

Deputy for Sci & Techlgy
Attn Ofc Asst Sec Army (R&D)
Washington DC 30210

Dir for MANPRINT
Ofc of the Deputy Chief of Staff for Prsnnl
Attn J Hiller
The Pentagon Rm 2C733
Washington DC 20301-0300

US Army ARDEC
Attn AMSTA-AR-TD M Fisette
Bldg 1
Picatinny Arsenal NJ 07806-5000

Commander
US Army CECOM
Attn AMSEL-RD-CZ-PS-B M Brundage
FT Monmouth NJ 07703-5000

US Army Info Sys Engrg Cmnd
Attn ASQB-OTD F Jenia
FT Huachuca AZ 85613-5300

US Army Natick RDEC
Acting Techl Dir
Attn SSCNC-T P Brandler
Natick MA 01760-5002

US Army Simulation, Train, & Instrmntn
  Cmnd
Attn J Stahl
12350 Research Parkway
Orlando FL 32826-3726

US Army Soldier & Biol Chem Cmnd Dir of
  Rsrch & Techlgy Dirctrt
Attn SMCCR-RS I G Resnick
Aberdeen Proving Ground MD 21010-5423

US Army Tank-Automtv Cmnd Rsrch, Dev, &
  Engrg Ctr
Attn AMSTA-TR J Chapin
Warren MI 48397-5000

US Army Train & Doctrine Cmnd
Battle Lab Integration & Techl Dirctrt
Attn ATCD-B J A Klevecz
FT Monroe VA 23651-5850

US Military Academy
Mathematical Sci Ctr of Excellence
Attn MDN-A LTC M D Phillips
Dept of Mathematical Sci Thayer Hall
West Point NY 10996-1786

Distribution (cont'd)

Nav Rsrch Lab
Attn Code 2627
Washington DC 20375-5000

Nav Surface Warfare Ctr A
Attn Code B07 J Pennella
17320 Dahlgren Rd Bldg 1470 Rm 1101
Dahlgren VA 22448-5100

Marine Corps Liaison Ofc
Attn AMSEL-LN-MC
FT Monmouth NJ 07703-5033

USAF Rome Lab Tech
Attn Corridor W Ste 262 RL SUL
26 Electr Pkwy Bldg 106
Griffiss AFB NY 13441-4514

DARPA
Attn S Welby
3701 N Fairfax Dr
Arlington VA 22203-1714

Hicks & Associates Inc
Attn G Singley III
1710 Goodrich Dr Ste 1300
McLean VA 22102

Palisades Inst for Rsrch Svc Inc
Attn E Carr
1745 Jefferson Davis Hwy Ste 500
Arlington VA 22202-3402

US Army Rsrch Ofc
Attn AMSRL-RO-EN W Bach
Attn AMSRL-RO-EN B Mann
Attn AMSRL-RO-D C Chang
PO Box 12211
Research Triangle Park NC 27709

US Army Rsrch Lab
Attn AMSRL-CI-AI-A Mail & Records Mgmt
Attn AMSRL-CI-AP Techl Pub (3 copies)
Attn AMSRL-CI-LL Techl Lib (3 copies)
Attn AMSRL-DC T Wolfenstine (15 copies)
Attn AMSRL-DD J M Miller
Attn AMSRL-SE-D E Scannell
Attn AMSRL-SE-DC S Gilman
Attn AMSRL-SE-E J Mait
Adelphi MD 20783-1197

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

1. AGENCY USE ONLY *(Leave blank)*	2. REPORT DATE March 2000	3. REPORT TYPE AND DATES COVERED Interim, Jan. 1 to Jan. 21 2000

4. TITLE AND SUBTITLE Predicted Discharge Rate for γ/β-MnO$_2$ versus λ-MnO$_2$	5. FUNDING NUMBERS DA PR: AH47 PE: 61102A
6. AUTHOR(S) Jeff Wolfenstine	

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory Attn: AMSRL-SE-DC email: jwolfenstine@arl.mil 2800 Powder Mill Road Adelphi, MD 20783-1197	8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TN-160

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory 2800 Powder Mill Road Adelphi, MD 20783-1197	10. SPONSORING/MONITORING AGENCY REPORT NUMBER

11. SUPPLEMENTARY NOTES
ARL PR: 9NENV1
AMS code: 611102.H47

12a. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited.	12b. DISTRIBUTION CODE

13. ABSTRACT *(Maximum 200 words)*

Recently, λ-MnO$_2$ has been proposed as an alternative cathode to γ/β-MnO$_2$ in Li/MnO$_2$ primary batteries because of its potential faster discharge rate. The results presented here suggest that (1) switching from γ/β-MnO$_2$ to λ-MnO$_2$ of equal particle size will lead to a maximum increase in the discharge rate at room temperature of about an order of magnitude and (2) when formed by acid digestion, γ-MnO$_2$ and β-MnO$_2$ have a higher lithium diffusivity and hence a faster discharge rate than when they are produced by the usual commercial means, a difference that may result from the lower structural water content in the materials produced by acid digestion.

14. SUBJECT TERMS Primary batteries, discharge rate, manganese dioxide	15. NUMBER OF PAGES 13
	16. PRICE CODE

17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT UL

7